



The Analysis of Fibre Properties of Water Retted *Sansevieria trifasciata* with Sodium Hydroxide

Bindu Kumari ^{a++*}, Lalita Rani ^{b#}, Nisha Arya ^{a†},
Sachin Kumari ^{c†} and Neeta Poonia ^{a++}

^a Department of Apparel and Textile Science, I.C. College of Community Science, Chaudhary Charan Singh Haryana Agricultural University, Hisar, India.

^b CCS HAU, Krishi Vigyan Kendra Kurukshetra-136118, India.

^c Department of Chemistry, College of Basic Science and Humanities CCS Haryana Agricultural University, Hisar, India.

Authors' contributions

This work was carried out in collaboration among all authors. All authors read and approved the final manuscript.

Article Information

DOI: 10.9734/IJPSS/2023/v35i214072

Open Peer Review History:

This journal follows the Advanced Open Peer Review policy. Identity of the Reviewers, Editor(s) and additional Reviewers, peer review comments, different versions of the manuscript, comments of the editors, etc are available here: <https://www.sdiarticle5.com/review-history/108556>

Original Research Article

Received: 29/08/2023

Accepted: 04/11/2023

Published: 09/11/2023

ABSTRACT

In the last decade, natural fibres have been in high demand because of their strength, high efficiency, and biodegradability easy availability for nature and improved textile properties than synthetic fibre. So, the increasing preference towards natural and green textile products rather than synthetic products has increased the attraction of tourists to the local as well as outside markets. Therefore, the present paper focused on the analysis of sodium hydroxide on the fibre properties of water-retted *S. trifasciata* (snake plant) fibres. The extraction of fibres from snake plant leaves was

⁺⁺ Research Scholar;

[#] District Extension Specialist (Home-Science);

[†] Asst. Professor;

*Corresponding author: E-mail: binduguri3@gmail.com;

conducted by using water water-retted method. Three different time periods were selected i.e. 10, 15 and 20 days for water retting. After water retting, the selected fibres were treated with an alkali i.e. NaOH. The optimum conditions for alkali were chemical concentration, material to liquor, time durations, treatment temperature and pH for standardization of the process of alkali treatment. The effect of sodium hydroxide was analyzed on fibre properties such as fibre yield, fineness, bundle strength, and elongation at the break. As a result, a gradual fibre yield was to be increased to decrease after being treated with alkali (NaOH). The alkali-treated fibres fibre yield, fineness and bundle strength was recorded (0.84 ± 0.02 g), (23.51 ± 0.39 denier) and (47.97 ± 0.13 g/tex). Elongation of the alkali-treated fibres was 5.02 ± 0.007 per cent. The resulting fibre properties were found suitable for other textile products such as apparel, reinforcement material composite etc.

Keywords: Green products; optimization; standardization; chemical treatment; water retted.

1. INTRODUCTION

Recent statistics revealed that the annual world production of natural fibers has been about 45.5 million tons; production of these fibers in India has been almost 14.5 million tons. Increasing consumption, especially in the developing countries, constraints on the natural resources required to produce fibers, and inability to increase the supply proportionate to the demand are expected to make most of the current fibers either too expensive or unavailable for commodity applications [1]. Recently, due to the improvement of people's living standards and need for environmental protection, the demand of natural biodegradable, sustainable, nontoxic and eco-friendly fibres is rising worldwide day by day. Ramie, flax, hemp and some other vegetable fibres have been used as textiles materials. But some plant yielding fibres species are still unexplored, these plant species can largely contribute to economic upliftment of local people through development of Research and Development programmes suitable for small scale industrialization. Natural fibres provide a number of benefits as compared to synthetic fibres, including low weight, low density, low cost, acceptable particular qualities, and the fact that they are recyclable and biodegradable. They're also renewable and have a good strength-to-stiffness ratio. Eco-friendly, biodegradable, and recyclable textile products are gaining popularity in the world market, bringing natural fibre into the spotlight. The earth is densely populated with a variety of plants that may have the potential to generate valuable fibres, but they have yet to be studied. Longer leafy plants appear to have a higher fibre generating capacity [2]. *Sansevieria trifasciata* leaf is found abundantly in India and this (family-Ruscaceae Agavaceae and genus-Sanseveria). *S. trifasciata* (Species) is an evergreen herbaceous perennial plant forming dense stands, spreading by way of its creeping

rhizome, which is sometimes above ground, sometimes underground. Its have stiff leaves grow vertically from a basal rosette and mature leaves are dark green with light gray-green cross-banding and usually range between 70-90cm in length and 5-6cm in width [3]. Retting of natural plant fibres is a microbiological process that removes non-cellulosic components such as pectin, hemicelluloses, lignin, waxes, and lipids and separates the fibre from plant materials. Hence microbial action requires both moisture and a warm temperature for degumming process (Hulle et al. 2015). Mechanical processing removes non-fibre components from individual fibres. Under-retting or insufficient retting gives poor results i.e. inadequate separation of non-fiber components (such as shive) from fibres, lowering fibre production, processing efficiency, and overall fibre quality. Over-retting, on the other hand, might result in poor fibre quality. In terms of fibre yield and quality, retting is critical (Brunsek et al., 2019). To optimize the conditions for fibre extraction from *S. trifasciata* (snake plant) using conventional degumming and analyze the fibre properties of extracted fibre.

2. METHODOLOGY

2.1 Materials

Matured green leafy leaves purchased from Agritourism Centre CCSHAU, Hisar, sodium hydroxide (NaOH), acetic acid (CH_3COOH), hydrogen chloride (HCl) chemicals used were of textile laboratory.

2.2 Methods

2.2.1 Collection of raw materials

Green matured *S. trifasciata* (snake plant) leaves were collected from the Agri-tourism centre of Chaudhary Charan Singh Haryana Agricultural University, Hisar.

2.2.2 Fibre extraction from *S. trifasciata* SPL

The fibres from *S. trifasciata* (snake plant) leaves were firstly extracted through water retting process.

2.2.3 Water retting process

10, 15 and 20 days of duration during the month of June and July with atmospheric temperature were used for water retting process and Changed the water after every two days. After 10, 15 and 20 days of duration, the fibres were separated from the biodegraded leaves by means of hand rubbing. The extracted fibres were washed with clean running water, dried at ambient temperature and weighed. On the basis of visual analysis, selected fibres for treatment with sodium hydroxide were 15 days.

2.3 Treatment of Water Retted *S. trifasciata* (Snake Plant) Leaves Fibres and Optimization Parameters of Treated *S. trifasciata* (Snake Plant) Leaves Fibres

Water retted fibres were subjected to alkali treatment at different parameters and conditions to assess the different fibre properties of the water retted *S. trifasciata* (snake plant) leaves fibres. The different parameters and conditions were i.e. 2.5, 5.0 and 7.5 g/L concentrations [4] of sodium hydroxide; 1:10, 1:20 and 1:30 material to liquor ratios at 80°, 90° and 100° C

temperature for 60, 90 and 120 minutes time duration [5] and 6, 7 and 8 pH. Alkali treated samples were sent to NITRA Ghaziabad, Uttar Pradesh and Central Institute of Research for Cotton Technology (CIRCOT), Sirsa for testing of physical and mechanical properties and the data was analyzed statistically.

Hence, the most suitable selected parameters were 5.0 g/l concentration of the solution, 1:20 material to liquor ratio, 90°C temperature, time 90 minutes and pH 7, respectively.

3. RESULTS AND DISCUSSION

3.1 Determination of Physical Characteristics of *S. trifasciata* (Snake Plant)

The physical characteristics [6] of the selected plant species (*S. trifasciata*) were determined and presented in Table 2. The average length of *S. trifasciata* (snake plant) leaves was found to be 71.92±3.84 cm. The width of the leaves [7] ranged from top edge 8.01±0.69 cm, in the middle portion 10.45±1.27 cm and from bottom edge was 6.64±0.64 cm. The average weight of smallest leaves and longest leaves was recorded to be 52.6±2.727 g and 68.8±1.166 g, respectively. The total numbers of leaves were 7 to 8 in a plant and weight of the whole plant was 2000-3000g approx. The maturity period of the leaves was about 2 to 3 month.



10 days retted *S. trifasciata* (snake plant) leaves fibres



15 days retted *S. trifasciata* (snake plant) leaves fibres



20 days retted *S. trifasciata* (snake plant) leaves fibres

Image 1. Water retted dried *S. trifasciata* (snake plant) leaves fibres

Table 1. Optimized selected parameters for alkali treatment

Parameters	Treatment	Sodium hydroxide (alkali)
Concentration (g/l)		5.0
Material to liquor ratio		1:20
Temperature (°C)		90
Time (minutes)		90
pH		7

Table 2. Physical characteristics of *S. trifasciata* (snake plant) 3

Physical characteristics	Measurements
Length of leaves (cm)	71.92±3.84
Width of leaves (cm)	
At the top	8.01±0.69
At the middle	10.45±1.27
At the bottom	6.64±0.64
Weight of leaves (g)	
Smallest leaves	52.6±2.727
Longest leaves	68.8±1.166
Number of leaves in a plant	7-8
Weight of the whole plant (g)	2000-3000 approx.
Maturity period of leaves (months)	2-3

* Mean and * Standard deviation (+ increase and - decrease values)

3.2 Optimization of Water Retting Process of *S. trifasciata* (Snake Plant) Leaves Fibres

In order to optimize the retting process for extracting *S. trifasciata* (snake plant) leaves fibres, three different time durations were selected i.e. 10, 15 and 20 days [8]. From the Table 3, it was evident that the yield of fibre after 15 days of retting was 260 g whereas the lowest yield was estimated i.e. 254 g after 20 days of retting. It was found that the quality of the fibres was good, soft and free from impurities after 15 days of retting. 15 days water retted fibres were selected for further treatment with alkali. It was observed that the 15 days water retted fibres were found more suitable for both treatments i.e. NaOH.

3.3 Effect of NaOH Concentration on Fibre Yield of *S. trifasciata* (Snake Plant) Leaves Fibres

It can be elicited that the water retted *S. trifasciata* (snake plant) leaves fibres were

treated with three different concentrations of NaOH solution i.e. 2.5, 5.0 and 7.5 g/l at 90° C. The treatment time was kept at 60, 90 and 120 minutes at 90° C and material to liquor ratio was taken 1:20. After various treatments the fibre yield was calculated. Fig. 1 showed the loss in weight of *S. trifasciata* (snake plant) leaves fibres after alkali treatment with different concentrations, time periods and pH. The fibre yield was calculated to estimate the quality of fibres obtained after alkali treatment. As the concentration of sodium hydroxide 2.5 to 7.5 g/l, there was a sharp increase in loss of fibre weight [9,10] percentage after applied of 2.5 g/l of NaOH concentration. As the concentration increased to 5.0 g/l of NaOH concentration, there was a marked increase in the weight loss of fibres. The weight loss of fibres also decreased with increased in time periods i.e. 60 to 90 minute then the fibre yield also increased from 0.87 to 1.00 per cent and weight decreased i.e. 0.78 per cent with pH 7 for 120 minutes. liquor ratio at 90°C using 5.0g/l of NaOH concentration at 90 minutes and pH 7.

Table 3. Observation recorded during water retting process

Material weight (Kg)	Bath ratio (M:L, g/L)	Time duration (days)	Temperature (°C)	Yield of fibre after drying (g)	Recorded Observation
12.5	1:70	10	41° C±2	258	Fibre was stiff with partial removal of fleshy and leaf portions
12.5	1:70	15	41° C±2	260	Fibre quality was good, soft and free from impurities
12.5	1:70	20	41° C±2	254	Fibre quality was good but lose the strength

Statistically, it was found that the effect of chemical concentrations at 2.5 and 5.0 g/l of NaOH concentrations was significant while at 7.5 g/l of NaOH concentration was non-significant at 5 per cent level of significance in respect of fibre yield. At 2.5 and 5.0 g/l of NaOH concentration, the mean and coefficient values were observed 0.84 ± 0.038 per cent with Coefficient Variance %-5.612 and 0.884 ± 0.025 per cent with Coefficient Variance %-3.475. Likewise, at 7.5 g/l of NaOH concentration was noticed to be 0.766 ± 0.090 per cent (Coefficient Variance %-14.420) with decreased fibre yield. A gradual decrease in fibre yield was reported after successive increase in alkali concentration.

3.4 Effect of NaOH Concentrations on Fibre Fineness of *S. trifasciata* (Snake Plant) Leaves Fibres

The data indicates that the water retted *S. trifasciata* (snake plant) leaves fibres were treated by using different chemical concentrations of alkali i.e. 2.5, 5.0 and 7.5 g/l of NaOH at different treatment times and pH of cooking bath. The fibres were digested with 2.5, 5.0 and 7.5 g/l of NaOH solution on the basis of material to ratio 1:20 for treatment times i.e. 60, 90 and 120 minutes with pH 6, 7 and 8 baths at 90° C. After each digestion, the fibres were washed and neutralized with acetic acid to free from chemical and then dried in hot oven. The fibres treated in 2.5 g/l of NaOH solution showed the minimum fibre fineness i.e. 69.78 to 40.72 denier as per treatment time periods with different pH of digestion, while fibres treated in 7.5 g/l of NaOH solution obtained the moderate fineness i.e. 68.75 to 45.91 denier (Fig. 2). The fibre fineness obtained to be 60.109 ± 6.236 denier with Coefficient Variance %-12.707 at 2.5 g/l of NaOH digestion for different time and pH, the fibres were inferior in quality. The fibre fineness was noticed to be 45.729 ± 11.923 denier with Coefficient Variance %-31.737 at 5.0 g/l NaOH solution and 58.588 ± 7.510 denier with Coefficient Variance %-15.698 at 7.5 g/l of NaOH solution, respectively. The quality of the fibres was obtained soft and with adequate handling properties. The fineness of fibres was observed at 2.5 g/l of NaOH solution, the fibres obtained were not soft enough to handle. At higher concentration of NaOH (7.5 g/l), the fibres were obtained much deteriorated. The effect of different concentration i.e. 2.5, 5.0 and 7.5 g/l, time 60, 90 and 120 minutes with pH 6, 7 and 8

were observed statistically non-significant at 5 per cent level of significance in respect of fibre fineness.

3.5 Effect of NaOH Concentrations on Bundle Strength of *S. trifasciata* (Snake Plant) Leaves Fibres

It is obvious from the results depicted in Fig. 3 that water retted *S. trifasciata* (snake plant) leaves fibres were treated by using different chemical concentration of alkali i.e. sodium hydroxide at different time and pH of cooking for bundle strength. The fibres were digested with 2.5, 5.0 and 7.5 g/l of NaOH solution keeping material to ratio 1:20 for 60, 90 and 120 minutes with pH 6, 7 and 8 at 90° C and 6 pH. The highest bundle strength [11] was discerned 49.29 g/tex at 5.0 g/l of NaOH concentration for 60 minutes time period at 90°C as compared to the fibres obtained lowest bundle strength i.e. 40.11 at 2.5 g/l of NaOH digestion for different time and pH 7. Probably, the bundle strength [12] got affected adversely at longer treatment time due to cellulose backbone being attacked along with the hemicelluloses and lignin. The colour of fibres was noticed greenish yellow, soft and smooth texture at 5.0 g/L concentration which was suitable for further extraction of fibres.

3.6 Effect of Concentration of Alkali on Elongation of *S. trifasciata* (Snake Plant) Leaves Fibre at 90° C

The shown data elucidates that when alkali treatment was carried out at 90°C boiling temperature, the elongation at break was decreased to increase at 2.5 g/l of sodium hydroxide concentrations at different time periods and pH. The fibres were digested with 2.5, 5.0 and 7.5 g/l on the basis of keeping material to ratio 1:20 (MLR) for treatment time periods i.e. 60, 90 and 120 minutes with pH i.e. 6, 7 and 8 at 90° C. After each digestion, the fibres were washed and neutralized to remove the excess chemical, and then dried in hot oven. The data indicates that the higher elongation (5.21 per cent) was found in case of 5.0 g/l of sodium hydroxide concentration followed by elongation 4.27 per cent at 90°C at different treatment time periods and pH (Fig. 4). Conclusively, it could be stated that the percentage of critical difference in the elongation was observed non-significant at 5 per cent level of significance.

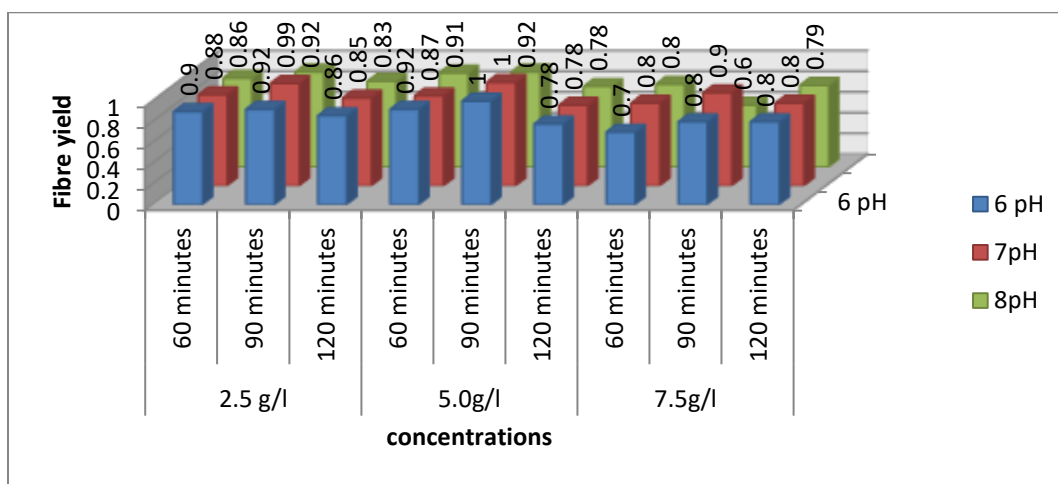


Fig. 1. Effect of NaOH concentration on fibre yield of *S. trifasciata* (snake plant) leaves fibres

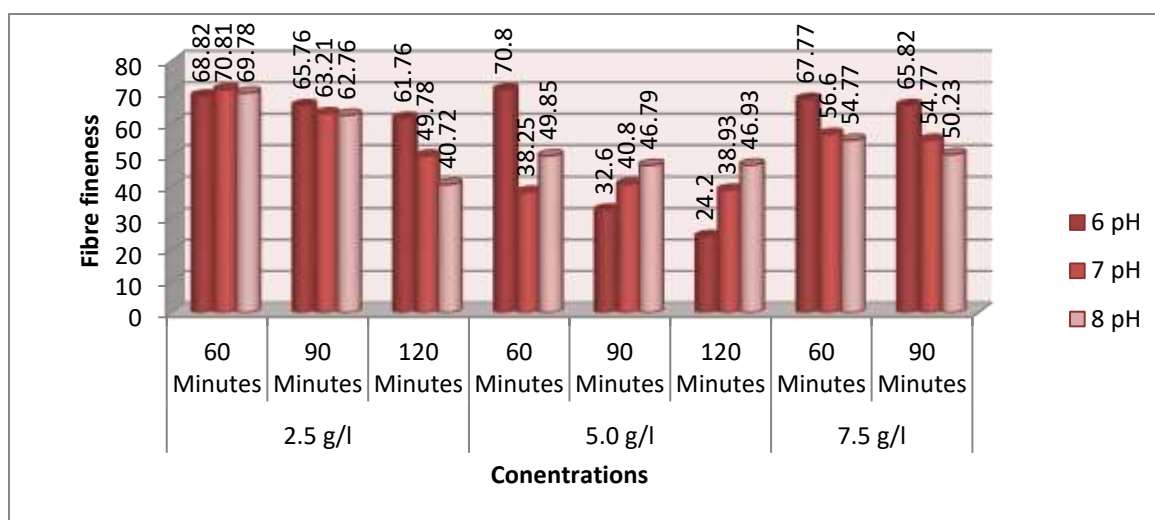


Fig. 2. Effect of NaOH concentrations on fibre fineness of *S. trifasciata* (snake plant) leaves fibres

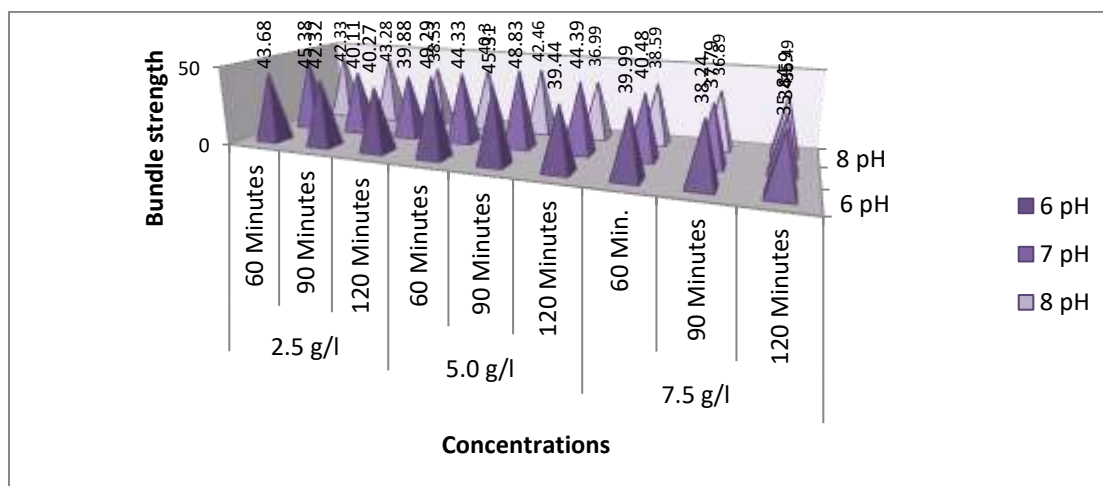


Fig. 3. Effect of NaOH concentrations on bundle strength of *S. trifasciata* (snake plant) leaves fibres

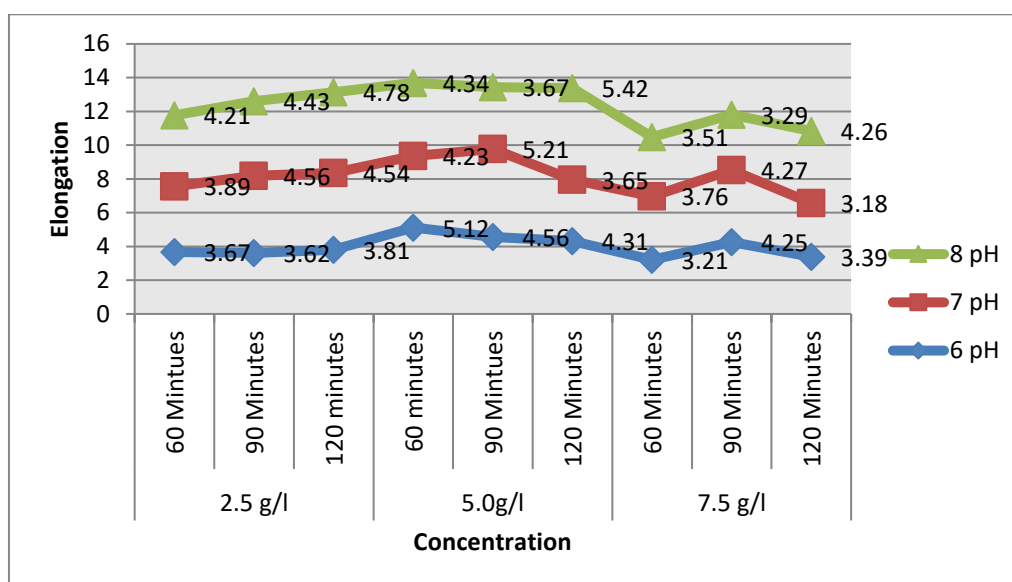


Fig. 4. Effect of concentration of alkali on elongation of *S. trifasciata* (snake plant) leaves fibre

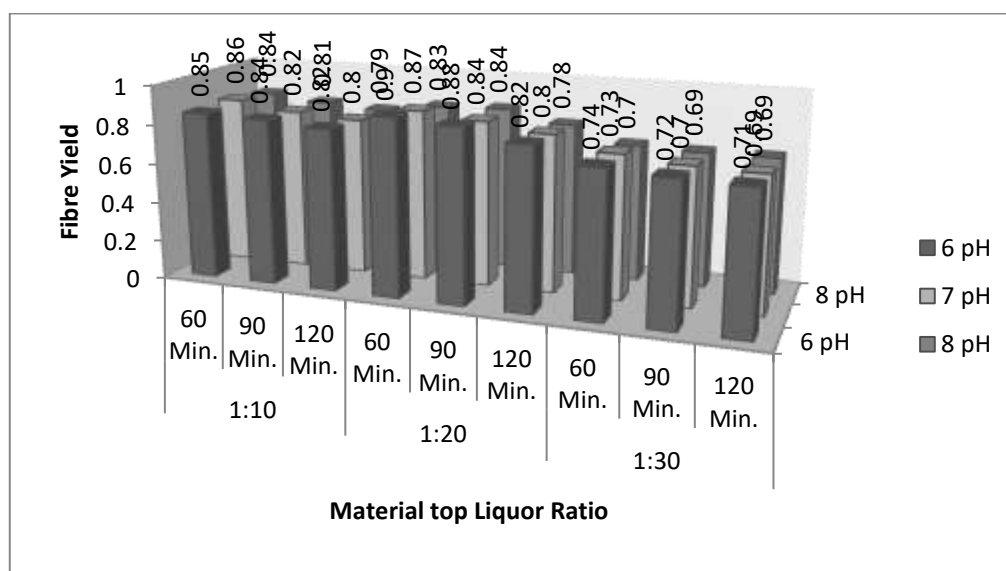


Fig. 5. Effect of material to liquor ratios of alkali on fibre yield of *S. trifasciata* (snake plant) leaves fibre

3.7 Effect of Material to Liquor Ratio With NaOH (5.0 g/L) on Fibre Yield of *S. trifasciata* (Snake Plant) Leaves Fibres at 90°C

The graphical representation (Fig. 5) indicates that the treatment of water retted *S. trifasciata* (snake plant) leaves fibres were carried out by using different material to liquor ratios (owf) i.e. 1:10, 1:20 and 1:30 with 5.0 g/l of NaOH concentration at different time and pH for fibre yields. The fibres were digested with 5.0 g/l of

NaOH solution at 90° C with different time i.e. 60, 90 and 120 minutes and pH 6, 7 and 8. The fibres were washed and neutralized to remove the excess amount of chemical after each digestion and then the fibres were dried in hot oven. It was evident that good quality of fibres were not obtained while digesting with 5.0g/l of NaOH concentration with bath ratio 1:30 at different time intervals and pH. Acceptable quality and fibre yield were obtained by digesting with 1:20 material to liquor ratio at 90°C using 5.0g/l of NaOH concentration at 90 minutes and pH 7.

3.8 Effect of Material to Liquor Ratio With NaOH (5.0 g/L) on Fibre Fineness of *S. trifasciata* (Snake Plant) Leaves Fibres at 90° C

The data presented data indicates that the treatment of water retted *S. trifasciata* (snake plant) leaves fibres were carried out at three different material to liquor ratios (owf) i.e. 1:10, 1:20 and 1:30 at three different time and pH of bath cooking in Fig. 6. The fibres were digested with 5.0 g/l of NaOH solution at different time 60, 90 and 120 minutes at 90° C with different pH 6, 7 and 8. The fibres were washed and neutralized to remove the excess quantity of chemical after each digestion and then the fibres were dried in hot oven. At 1:10 material to liquor ratio, the maximum fibre fineness was noticed to be 46.06±7.106 denier with Coefficient Variance %-18.894. After increasing chemical concentration it was recorded the fibre fineness was decreased 43.997±2.488 denier with Coefficient Variance %- 6.926 at 5.0 g/l of NaOH concentration to 53.993±2.991 with Coefficient Variance %- 6.785 at 7.5 g/l of NaOH concentration given to water retted fibres. Different alkali treatments had a change in fibre fineness of treated SPL fibres which was non-significant at 5% level of significance at 1:10 and 1:30 material to liquor

ratio. At 1:30 material to liquor ratio, the fibre fineness of treated fibres was significant at 5per cent level of significance.

3.9 Effect of Material to Liquor Ratio with NaOH (5.0 g/L) on Bundle Strength of *S. trifasciata* (Snake Plant) Leaves Fibres at 90° C

It can be elucidated that the water retted *S. trifasciata* (snake plant) leaves fibres were treated by using different material to liquor ratios for alkali treatment at 90°C. The different material to liquor ratios (owf) were used i.e. 1:10, 1:20 and 1:30 with 5.0 g/l of NaOH for different time duration 60, 90 and 120 minutes and pH 6, 7 and 8 at 90° C (Fig. 7). It is evident from the table that at 1:10 material to liquor ratio, the highest mean value for bundle strength was found to be 45.092±2.006 g/tex with Coefficient Variance %-5.449. As the material to liquor continuously decreased from 1:20 to 1:30 (MLR), the bundle strength was decreased from 43.663±4.467g/tex with Coefficient Variance %-12.531 to 37.204±3.097g/tex with Coefficient Variance %- 10.194. As a result, the bundle strength of SPL fibres decreased with increasing of material to liquor ratio, time and temperature of treatment.

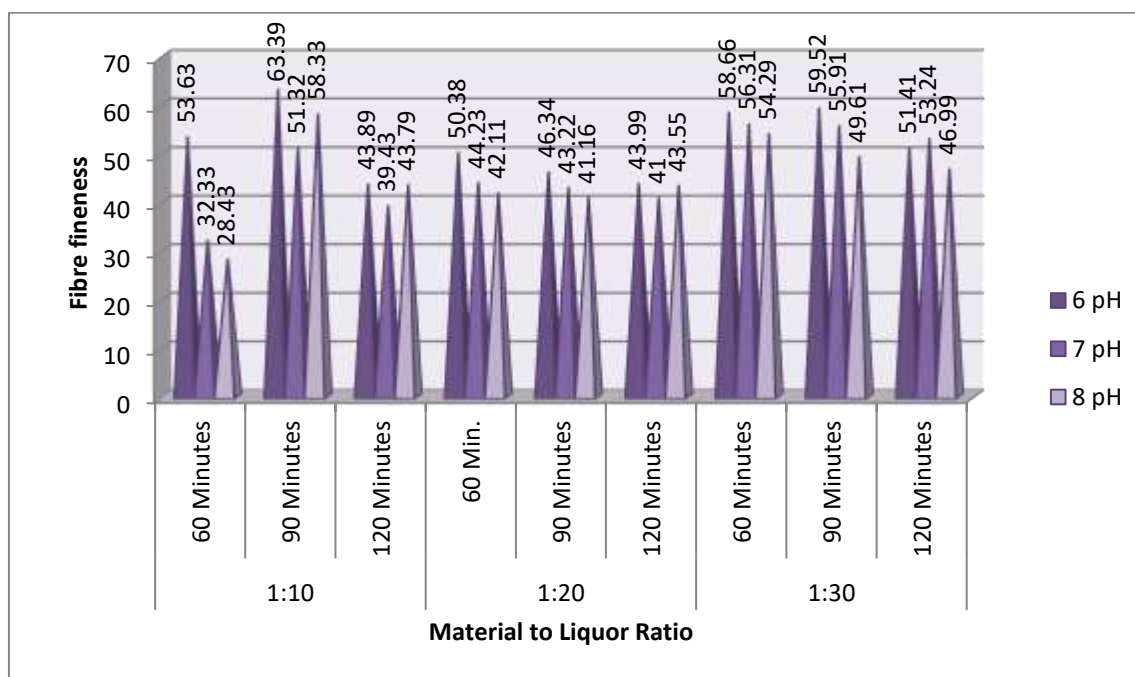


Fig. 6. Effect of material to liquor ratios of alkali on fibre fineness of *S. trifasciata* (snake plant) leaves fibre

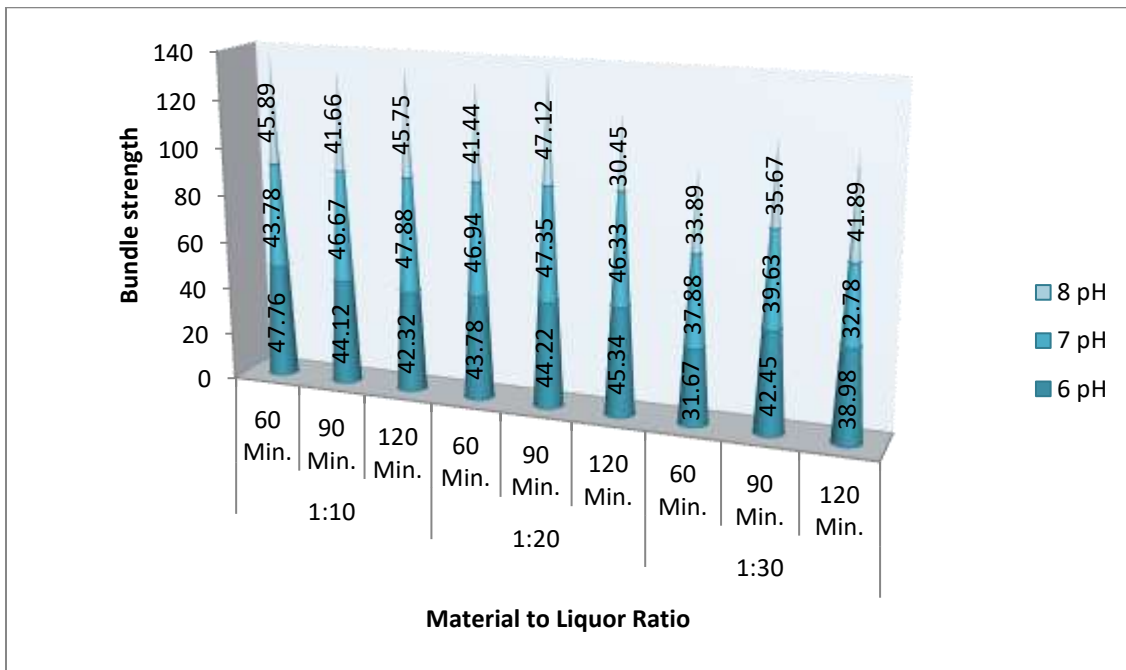


Fig. 7. Effect of material to liquor ratios of alkali on bundle strength of *S. trifasciata* (snake plant) leaves fibre

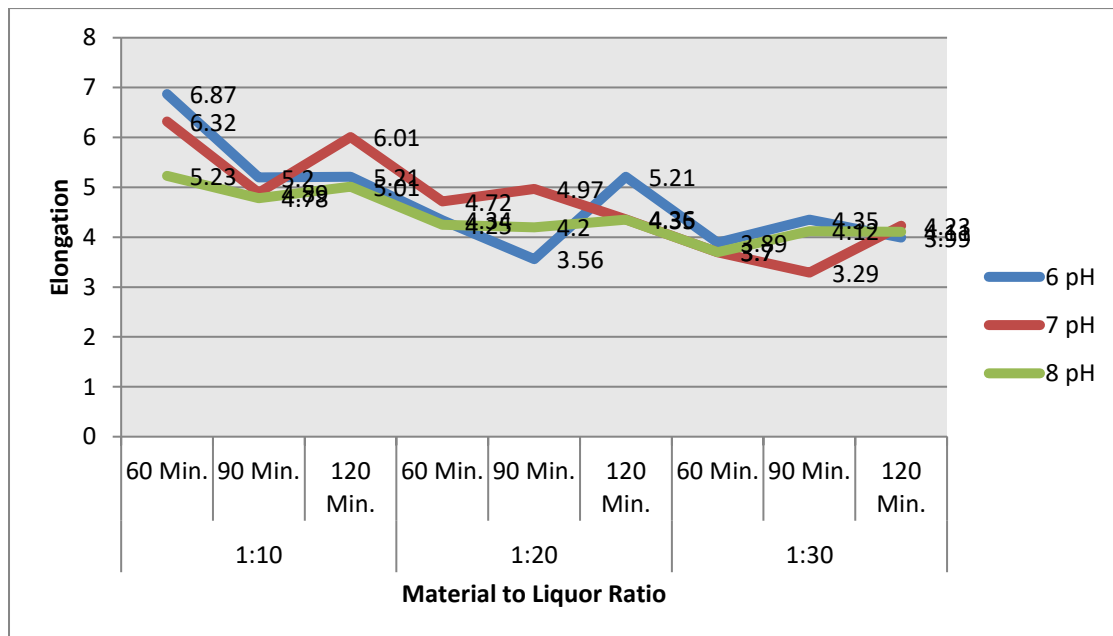


Fig. 8. Effect of material to liquor ratios of alkali on elongation of *S. trifasciata* (snake plant) leaves fibre

3.9 Effect of Material to Liquor Ratio with NaOH (5.0 g/L) on Bundle Strength of *S. trifasciata* (Snake Plant) Leaves Fibres at 90° C

It can be elucidated that the water retted *S. trifasciata* (snake plant) leaves fibres were

treated by using different material to liquor ratios for alkali treatment at 90°C. The different material to liquor ratios (owf) were used i.e. 1:10, 1:20 and 1:30 with 5.0 g/l of NaOH for different time duration 60, 90 and 120 minutes and pH 6, 7 and 8 at 90° C (Fig. 7). It is evident from the table that at 1:10 material to liquor ratio, the highest mean

value for bundle strength was found to be 45.092 ± 2.006 g/tex with Coefficient Variance %-5.449. As the material to liquor continuously decreased from 1:20 to 1:30 (MLR), the bundle strength was decreased from 43.663 ± 4.467 g/tex with Coefficient Variance %-12.531 to 37.204 ± 3.097 g/tex with Coefficient Variance %-10.194. As a result, the bundle strength of SPL fibres decreased with increasing of material to liquor ratio, time and temperature of treatment.

4. CONCLUSION

Results of this study have proven that the non-conventional plant material such as *S. trifasciata* (snake plant) is ideal source for fibre extraction. Water retting is the best for natural plants to extract the fibres. The presented data was tested by NITRA Ghaziabad, Uttar Pradesh and Central Institute of Research for Cotton Technology (CIRCOT), Sirsa for testing of physical and mechanical properties. The fibre properties i.e. fibre yield, fineness, bundle strength, elongation were tested with three different parameters. It was noted that at concentration of 5.0 g/l sodium hydroxide with 1:20 material to liquor ratio and a temperature of 90°C for 90 minutes with pH 7 for alkali treatment were found to enhance the fibre properties of *S. trifasciata* (snake plant) leaves fibres.

DATA AVAILABILITY

The research data used to support the findings of this study are included in the article. Data in figures and table formats are included within the article and also provided in separate MS-Word format. Additional data used to support the findings of this study will be available from the corresponding author upon request. Apart from the data collected from experiments previously reported data were used to support this study and are cited at relevant places within the text as references.

CONFLICT OF INTEREST

The authors declared no potential conflicts of interest with respect to the research, authorship and publication of this article. All authors agree that the contents of the manuscript are confidential and will not be copyrighted submitted or published elsewhere in any language.

ACKNOWLEDGEMENT

Authors are thankful to the Chaudhary Charan Singh Haryana Agricultural University (CCSHAU) for providing lab facilities to conduct research. The corresponding author is thankful to the other authors and to the Suman, Sandeep and Abinaya S. for providing valuable inputs in the manuscript formation and revision. The authors received no financial support for the research work and publication of this article.

REFERENCES

1. Kanimozhi M. Extraction, fabrication and evaluation of *Sansevieria trifasciata* fiber. Indian Journal of Applied Research. 2011; 1(2):97-98.
2. Kant R, Alagh P. Extraction of fibre from *Sansaviera trifaciata* plant and its properties. International Journal of Science and Research. 2015;4(7):2547-49.
3. Kumar MA, Reddy GR, Reddy GH, Chakradhar KVP, Reddy N. Mechanical properties of randomly oriented short *Sansevieria trifasciata* fibre/epoxy composites. International Journal of Fiber and Textile Research. 2011;1(1): 6-10.
4. Amanuel L. Palm leaf sheath fiber extraction and surface modification. Journal of Engineered Fibers and Fabrics. 2020;15(6):1-6.
5. Wang WM, Cai ZS, Yu JY. Study on the chemical modification process of jute fiber. Journal of Engineered Fibers and Fabrics. 2008; 3(2):1-11.
6. Msahli S, Rezig S, Jaouadi M, Khoffi F, Durand B. Optimization of extraction process of *Typha* leaf fibres. Indian Journal of Fibre and Textile Research. 2016; 41(7):242-48.
7. Widyasanti A, Napitupulu LOB, Thoriq A. Physical and mechanical properties of natural fibre from *Sansevieria trifasciata* and *Agave sislana*. Earth and Environmental Science. 2020;462(3): 1-11.
8. Garima. Standardization of condition for extraction of fibre from corn stover. Master's Thesis, Department of Textile and Apparel Designing, Punjab Agricultural University, Ludhiana; 2017.
9. Jain A, Rastogi D, Chanana B, Parmar MS. Extraction of cornhusk fibres for textile usages. Journal of Polymer and Textile Engineering. 2017;4(1):29-34.

10. Zannen S, Ghali L, Halimi MT, Hssen MB. Effect of chemical extraction on physicochemical and mechanical properties of Doum Palm fibres. *Advances Materials Physics and Chemistry*. 2014; 4(10):203-16.
11. Nalankalli G, Saravanan D, Govindaraj N, Harish P. Efficacy of solvent, alkali and pectinase on the removal of non-cellulosic from cotton fibres. *Indian Journal of Fiber and Textile Research*. 2008;33(4):438-42.
12. Samanta AK, Singhee D, Basu G, Biswas SK. Thermal behavior and structural features of chemically and biochemically modified jute substrate. *Indian Journal of Fibre and Textile Research*. 2007;32(2): 355-65.

© 2023 Kumari et al.; This is an Open Access article distributed under the terms of the Creative Commons Attribution License (<http://creativecommons.org/licenses/by/4.0>), which permits unrestricted use, distribution, and reproduction in any medium, provided the original work is properly cited.

Peer-review history:

The peer review history for this paper can be accessed here:
<https://www.sdiarticle5.com/review-history/108556>